



Impact of Thermal Treatment on Anatomical and Mechanical Properties of *Ricinodendron heudelotii* Wood

E. A. Iyiola^{1*}, S. O. Ayanleye¹, O. Catherine¹, B. Olufemi¹, F. A. Faruwa²
and A. Wekesa³

¹Department of Forestry and Wood Technology, Federal University of Technology, P.M.B. 704, Akure, Nigeria.

²Department of Forestry and Wildlife Management, Federal University of Technology, P.M.B. 1526, Owerri, Nigeria.

³Department of Agroforestry and Rural Development, University of Kabianga, P.O.Box 2030 -20200, Kericho, Kenya.

Authors' contributions

This work was carried out in collaboration among all authors. Authors EAI and CO designed the study, performed the statistical analysis and wrote the first draft of the manuscript. Authors BO, FAF and AW managed the analyses of the study. Author SOA managed the literature searches and wrote the second and final draft of the manuscript. All authors read and approved the final manuscript.

Article Information

DOI: 10.9734/JSRR/2019/v22i530101

Editor(s):

(1) Dr. Tzasna Hernandez Delgado, Laboratory of Pharmacognosie, Unidad de Biología y Prototipos (UBIPRO), Facultad de Estudios Superiores Iztacala, Universidad Nacional Autónoma de México, México.

Reviewers:

(1) J. Dario Aristizabal-Ochoa, National University of Colombia At Medellin, Colombia.

(2) Ali Abdul-Aziz, Kent State University, USA.

Complete Peer review History: <http://www.sdiarticle3.com/review-history/48186>

Original Research Article

Received 07 January 2019

Accepted 20 March 2019

Published 26 March 2019

ABSTRACT

The study examined the impact of thermal treatment on anatomical and mechanical properties *Ricinodendron heudelotii* wood. Wood samples were oven dried at 105°C and cooled in a desiccator to a constant weight before the thermal treatment. Heat treatment of wood was carried out in a Furnace at 120°C, 140°C and 160°C for 45 minutes and 90 minutes. The Density, Modulus of Elasticity (MOE), Modulus of Rupture (MOR), and the anatomical properties were assessed. The results for Density of *Ricinodendron heudelotii* wood showed decrease from 279 kg/m³ (120°C at 45 minutes) to 256 kg/m³ (160°C at 90 minutes) while that of control was 281 kg/m³ which was lower than the treated samples. The increase in temperature with time had effect of the color of

*Corresponding author: E-mail: eaiyiola@futa.edu.ng;

wood as it changed from creamy white to dark brown. The image of untreated and treated samples showed no significant changes within and among treatment groups as there was no effect of treatment time and exposure on the samples.

The MOE of heat treated *Ricinodendron heudelotii* increased from 2064.84 N/mm² (140°C for 45 minutes) to 2271.93 N/mm² (160°C for 90 minutes) while MOR decreased from 40.56 N/mm² (140°C for 90 minutes) to 33.53 N/mm² (160°C for 90 minutes). The study revealed that the wood could be used in a light furniture as unnecessarily heavy wood is not important. Also, the study proved effective in improving the modulus of elasticity of the wood.

Keywords: Mechanical properties; *Ricinodendron heudelotii*; heat treatment; colour; density.

1. INTRODUCTION

Wood as a renewable natural resource has been used by man for thousands of years since his appearance on Earth and has contributed to his survival and to the development of civilization. For many reasons, the natural wood properties of some species do not give adequate performance which necessitate modification of the material [1].

Wood is a complex polymeric material which consists mainly of cellulose, hemicellulose and lignin with a minor quantity of extractives. The exposure of wood to elevated temperatures causes thermal degradation of its structure such as degradation of hemicellulose often accompanied by loss of mass and thus modifying the properties of wood. Thermal degradation is utilized commercially to produce wood products with improved dimensional stability and reduced hygroscopicity [2].

Wood is a hygroscopic material which is capable of losing and gaining moisture due to the fact that the cell wall polymers contain hydroxyl groups. In an environment containing moisture, dry wood will absorb moisture until it reaches equilibrium with the surrounding atmosphere. Similarly, saturated wood when placed in an atmosphere of lower relative humidity (H) will lose moisture until equilibrium is attained. If the wood is placed in an environment where the relative humidity is stable, it will attain constant moisture content which is known as the equilibrium moisture content (M_{emc}). At this point, the wood no longer loses or gain moisture. After treatment at 180°C or above, there is chemical changes in lignin and hemicelluloses of the treated wood making it to be less hygroscopic.

Wood modification can be defined as a process that improves the properties of wood by producing a new material that when disposed at the end of the product life cycle doesn't present an environmental hazard any greater than

unmodified wood [3]. However, the thermal modification of wood is defined as the application of heat to wood to cause a desired improvement in the properties of the material. Thermal modification is invariably performed between the temperature of 180°C and 260°C with temperature lower than 140°C resulting in only a slight change in the material properties. Temperature is one of the most important parameters responsible for the effect of modification in heat treated wood [4,5].

In hardwood, the cells that make up the anatomical organization are the vessels, parenchyma cells, fibres and the wood rays, although, fibres are the main element that is responsible for the strength of the wood [6]. Wood density is one of the most important wood property and indicator of strength for solid wood and fibre products [7]. It is usually affected by the cell wall thickness, the cell diameter, the earlywood to latewood ratio and the chemical composition of the wood [8]. Philips [9] reported that wood density is a measure of the cell wall material per unit volume and as such gives a very good indication of the strength properties and expected pulp yields of timber [9]. In softwood, the cells that make up the anatomical organization are the vessels, fibres, parenchyma cells and the wood rays. Fibres are the principal element that is responsible for the strength of the wood same as hardwood [6]. Wood density is an important wood property for solid wood and fibre products, it is one of the most important properties influencing the quality of a timber [7].

Variation in anatomical properties is therefore not observed only from one species to the other but also within the same species, within a tree, and also between the core wood of the tree and the outer wood [10]. According to Boonstra et al. [11] heat treatment affects the anatomical structure of wood but this effect depends on the wood species and the process parameters used. Softwood species are the most susceptible to

tangential cracks in the latewood section, especially with narrow annual rings and/or an abrupt transition between earlywood and latewood.

2. MATERIALS AND METHODS

2.1 Sample Size and Collection of Samples

Ricinodendron heudelotii belongs to the Euphorbiaceae family. It grows in tropical Africa from Guinea to Angola, East Africa and Madagascar in Cameroon. *Ricinodendron heudelotii* log was obtained from a local sawmill in Akure, Ondo State, Nigeria. The lumbers were air-dried to approximately 20% moisture content and cut along and across the grain with a Circular sawing machine to get the heat treatment specimens. Twenty-eight defect-free specimens of 20 × 20 × 10 mm were prepared for the evaluation of Density and weight loss according to ASTM standards.

2.2 Material Preparation

2.2.1 Sample preparation

For the evaluation of static bending strength tests (Modulus of rupture and Modulus of elasticity), twenty-eight specimens of 300 mm × 20 mm × 20 mm were prepared. A total of 56 specimens of both treated and untreated were prepared and properly labelled for the study. The specimens were oven dried at 103± 2°C until constant weight was achieved and then cooled in a desiccator containing silica gel to obtain the final weight. The wet weight and dry weight was estimated with a weighing balance of model H-1117 in the laboratory.

For anatomical samples, a radial sample of 1cm thickness was cut from the sample and then spitted using a blunt knife along the radial and tangential planes to make blocks in anatomical orientation, this orientation facilitates microtome sectioning. The radial sample was softened by immersion in water for hours (marked with a soft pencil) until it sinks under its own weight. Thin section was then taken from the three oriented planes: Tangential, transverse and radial section using a microtome sliding machine. It was placed in a petri-dish containing methylated spirit for moistening and also to prevent rolling and flaking character of the wood section. Staining was done by adding drops of safranin solution to the sections in the petri-dish and left for few minutes.

2.2.2 Slide preparation

After the microtome sample has been stained with safranin solution for few minutes, it was rinsed with water and alcohol until the excess stain was removed. It was dehydrated using ethanol and then placed on slide using forceps while the rough edges were also trimmed. Improvised Canada balsam was added to ensure clarity and was covered with coverslip (microscopic coverslip). Heat was finally applied to expel air bubbles from the prepared samples. Slide was then observed under a microscope.

2.2.3 Maceration process

Each wood sample was cut to slivers about 1mm thick and 1-2 cm in length and then subjected to maceration process. The sliver of each specimen was placed in a test tube and immersed with a mixture of acetic acid and hydrogen peroxide. The tubes and its contents were placed in an oven at 60°C for 48 hours, removed after 48 hours from the oven and washed thoroughly with water to remove acids from the process. The treated slivers were subjected to shaking to obtain more individual fibres. The macerated fibres were washed with distilled water and individual fibers were separated on slides, it was then measured under a microscope. All fibers were determined by Leica Image Analyzer System to get the *Fibre Length*, *Fibre diameter* and *Fibre lumen*.

2.3 Thermal Treatment Process

The heat treatment was conducted in a Muffle furnace with a temperature-controlled heating unit. The conditioned specimens (at constant M.C. of 12%) were thermally treated at temperatures of 120°C, 140°C and 160°C for the duration of 45 and 90 minutes each. The temperature of the furnace was ramped to the temperature at which the actual heat treatment occurred before introducing the wood samples. At the end of each treatment period, the samples were removed from the furnace followed by weight and dimension estimation after cooling in a desiccator with a silica gel to account for the weight change.

2.3.1 Moisture content determination

Therefore, the weight and dimension of all specimens were measured to determine the moisture content (MC) using:

$$MC (\%) = \frac{\text{wet weight} - \text{oven dry weight}}{\text{oven dry weight}} \times 100 \quad (1)$$

Where,

W_o (g) = the oven-dry weight of specimens before the treatment and

W_t (g) = the oven-dry weight of specimens after the treatment.

The percentage weight loss (PWL) was determined using:

$$WL (\%) = \left(\frac{W_o - W_t}{W_o} \right) \times 100 \quad (2)$$

Where,

W_o (g) is the oven dry weight of specimens before the treatment;

W_t is the dry weight of specimens after treated with heat

2.3.2 Density determination

Density is defined as the mass per unit volume of a material. Samples of 20 mm x 20 mm x 60 mm was cut for density determination. After cutting, the wood samples were weighed on the weighing balance to estimate the green weight; the samples were oven-dried at 103±2°C for 24 hours until the weight remained constant. The density ρ of the wood species was determined using;

$$\rho = \frac{M}{V} \quad (\text{kg/m}^3) \quad (3)$$

Where,

M= Mass (kg) and V= Volume (m³)

2.3.3 Mechanical properties

The Modulus of elasticity (MOE) and Modulus of rupture (MOR) was evaluated by subjecting samples of 20 mm x 20 mm x 300 mm to a force/load on the Universal Testing machine. All samples were supported by metal bearing plates to prevent damage to the beam at the point of contact between specimen and reaction support. At the point of failure, the force exerted on the specimen that caused the failure was recorded, the MOE and MOR was calculated using.

2.3.3.1 Moduli of elasticity and rupture

$$MOE = \frac{PL^3}{4bd^3D} \quad (4)$$

$$MOR = \frac{3PL}{2bd^2} (N/mm^2) \quad (5)$$

Where, L= Length of specimen between the machine supports (mm); b= Width of the specimen (mm); d = thickness of the specimen (mm); P = Ultimate load (N); and D = Axial deformation

2.4 Statistical Analysis

The experimental design for the study was a 2x3 Factorial experiment in Completely Randomized Design, the experiment was designed to include the predictor variables; Factor A (temperature) and Factor B (time). Data was analyzed using descriptive statistics, general linear model and univariate Post Hoc Test at logistic regression at 0.05.

3. RESULTS AND DISCUSSION

3.1 Color

For both maximum temperatures tested, *Ricinodendron heudelotii* woods became darker at 160°C 90 minutes of treatment. The changes in color were higher with elevated temperature and this is in accordance with the report of previous researchers [12] who assessed the color changes of oven heat treated *Leucaena leucocephala* and scot pine at elevated temperatures. The authors reported that heat-treated wood at temperatures above 160°C acquired darker tonality. Heat treatment improved some wood properties such as color being a good approach to improve low market valued tropical woods [13]. According to Sundqvist [14], the changes in color of thermally modified wood are attributed to oxidative changes which predominate over hydrolysis reactions. The effect of extractives in the color of heat-treated wood showed that unextracted and acetone extractives had varying color [14]. The report by Sundqvist asserted that both extractives and structural components such as hemicelluloses and lignin took part in color change of heat-treated wood.

3.2 Density Determination

The mean value of *Ricinodendron heudelotii* wood decreases from 279 kg/m³ (120 °C at 45 minutes) to 256 kg/m³ (160°C at 90 minutes) while that of control was 281 kg/m³ as shown in Fig. 1. The density of the treated samples were lower compared to control samples. It was observed that the density of wood samples decreases with time of exposure to heat treatment. The results were presented in Fig. 1

as density decreases with elevated temperature. Heat treatment increase mass loss due to the release of by-products from the wood during thermal degradation of lignin and as a result of the evacuation of volatile compounds which reduces the density of wood [12].

3.3 Mass Loss

The mean value of the mass loss for *Ricinodendron heudelotii* wood increased from 3.35% (120°C at 45 minutes) to 5.57% (160°C at 90 minutes) in Fig. 2. The mass loss of treated wood samples was higher as the temperature increased with time. It was observed that higher temperature and time has a

significant effect on mass loss. Mass loss in wood increases with increasing temperature or treatment time which was consistent with previous study [15,16].

3.4 Mechanical Properties

3.4.1 Moduli of elasticity and rupture

Modulus of elasticity (MOE) implies that deformations produced by low stress are completely recoverable after loads are removed. The MOE of heat treated *Ricinodendron heudelotii* increased from 2064.84 N/mm² (140°C for 45 minutes) to 2271.93 N/mm² (160°C for 90 minutes).

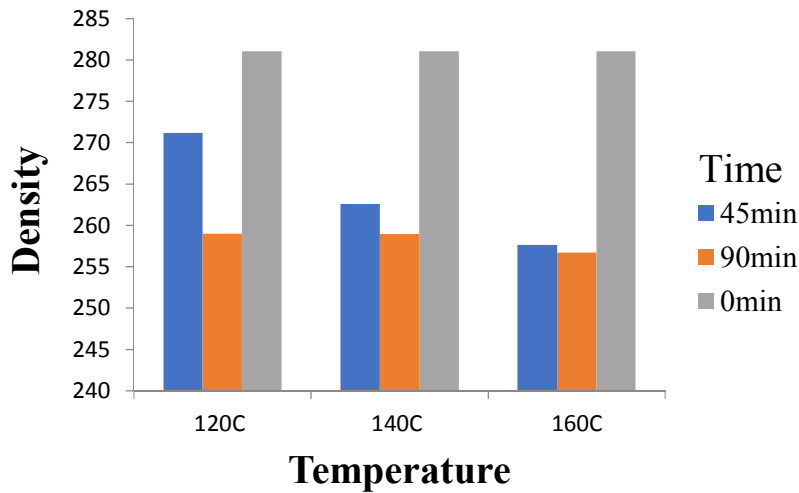


Fig. 1. Mean values of density of thermally treated *Ricinodendron heudelotii*


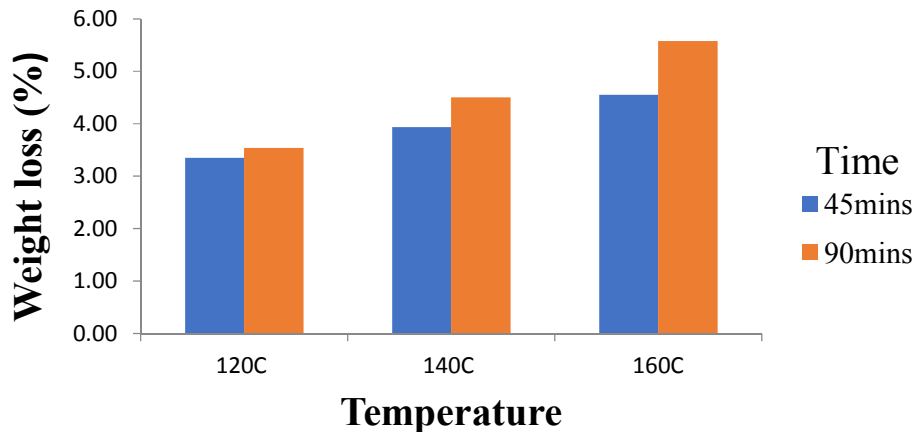



Fig. 2. Mean values of weight loss (%) of thermally treated *Ricinodendron heudelotii*

Modulus of rupture reflects the maximum load carrying capacity of a member in bending and is proportional to maximum moment or force borne by the specimen. The variation in the MOR of thermally treated *Ricinodendron heudelotii*

ranged from 40.56 N/mm² (140°C for 90 minutes) to 33.53 N/mm² (160°C for 90 minutes). MOR of the samples therefore declined with increasing temperature and time in a pattern that was consistent with the previous studies [17,18,19].

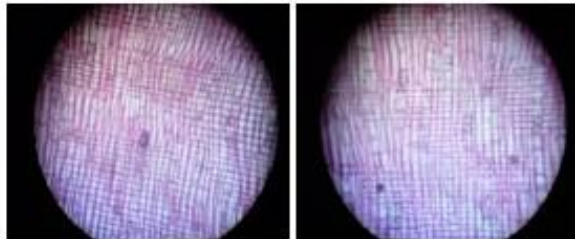

(a) 120⁰ C for 45 mins and 90 mins in Tangential plane

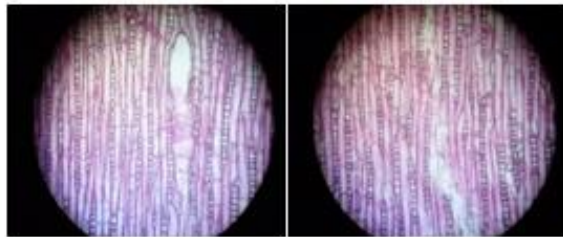

(b) 140⁰ C for 45 mins and 90 mins in Radial plane



(c) 160⁰C for 45 mins and control sample

Fig. 3. SEM images of the three sections of untreated *Ricinodendron heudelotii* wood and samples thermally modified at 120, 140 and 160°C and at 45 and 90 minutes each. Arrow showing crystal in *Ricinodendron heudelotii* wood

Table 1. Density, weight loss (%) and moisture content of *Ricinodendron heudelotii* wood at different temperature and pressure

Temp	Time	Density(Kg/m ³)	Weight loss (%)	MC(%)
0	0	281.06	0	6.82
120	45	271.16	13.39	3.47
120	90	259.02	14.16	3.75
140	45	262.59	15.73	4.09
140	90	258.94	18.02	4.77
160	45	257.64	18.21	4.94
160	90	256.71	22.28	6.23

Table 2. Modulus of Elasticity (MOE) and Modulus of Rupture (MOR) of *Ricinodendron heudelotii* at different temperature and pressure

Temp	Time	MOE(N/mm ²)	MOR (N/mm ²)
0	0	2173.575	37.59422
120	45	2127.808	35.52422
120	90	2144.686	41.42156
140	45	2064.84	38.84484
140	90	2149.611	40.55906
160	45	2217.154	33.66984
160	90	2271.928	33.52969

Table 3. Fiber length (FL), Fiber diameter (FD), Lumen width (LW), Cell wall thickness (CWT), Runkel ratio (RR), Flexibility coefficient (FL), and Slenderness of the fibre (SF)

Temp	Time	Fibre length	Fibre diameter	Lumen width	Cell wall thickness	Runkel ratio	flexibility coefficient	slenderness of the fibre
0	0	1.56	0.41	0.32	0.04	0.28	78.03	3.82
120	45	1.70	0.55	0.33	0.11	0.65	60.55	3.13
120	90	1.65	0.53	0.40	0.06	0.32	75.87	3.14
140	45	1.61	0.53	0.34	0.10	0.56	63.90	3.06
140	90	1.64	0.50	0.30	0.10	0.68	59.60	3.29
160	45	1.71	0.54	0.42	0.06	0.28	78.32	3.19
160	90	1.63	0.54	0.43	0.05	0.24	80.44	3.05

3.5 Anatomical Properties

Microscopic investigations were performed on each treatment group in the three planes that is, the transverse, tangential and radial plane to better understand the effect of elevated temperatures on the anatomical properties of wood. Images of untreated and treated wood are shown in Fig. 3 for comparism, although no significant change was noticed within and among treatment groups.

No significant changes were noted in the structure of the fibrous and parenchymatous tissues.

4. CONCLUSIONS

The thermal modification negatively affect the density and improve the modulus of elasticity of *Ricinodendron heudelotii* wood. The mass loss increases with increase in temperature and time. Heat treatment decreased wood density and increased the weight loss of the species. The degree of thermal modification effects depends on the treatment conditions (temperature and time).

The color of the wood changed from creamy white to dark brown with increasing treatment temperature and duration. Based on the results obtained from this research, heat treated wood

has greater dimensional stability than the untreated wood. The effect of thermal modification on ray parenchyma width requires further investigation.

The qualitative analysis using SEM indicated that no significant changes occurred in the structure of ray parenchyma, vessels and fibers tissues. Even crystals were preserved in the vessel elements of thermally modified wood at the highest processing temperature (160°C) and no quantitative changes were observed in the dimensions of fibers.

COMPETING INTERESTS

Authors have declared that no competing interests exist.

REFERENCES

1. Ajuziogu GC, Nwosu MO, Nzekwe U, Onyeke CC, Odo GE, Nwosu PM, Onyeonagu CC. Biomechanics, an aspect of the relationship between wood anatomical parameters and mechanical strength in ten Nigerian timber species. *International Journal of Scientific and Engineering Research*. 2014;5(2):629–645.
2. Akyildizh MH, Ates S. Effect of Heat Treatment on Equilibrium Moisture Content

- (EMC) of some Wood Species in Turkey. Research Journal of Agriculture and Biological Sciences. 2008;4(6): 660-665.
3. Hill C. Wood modification: Chemical, thermal and other processes. Wiley series in Renewables Resources, John Wiley and Sons Ltd; 2006.
 4. Mitchell MD, Denne MP. Variation in density of *Picea sitchensis* in relation to within tree trends in tracheid diameter and wall thickness. Forestry. 1997;70(1).
 5. Korkut DS, Guller B. The effects of heat treatment on physical properties and surface roughness of red-bud maple (*Acer trautvetteri* Medw.) wood. Bioresource Technology. 2008;99(8):2846–51.
 6. Panshin AJ, Zeeuw C. Textbook of wood technology. 4ed. NY: McGraw-Hill. 1980; 722.
 7. De Guth EB. Relationship between wood density and tree diameter in *Pinus elliottii* of *Missiones argentina*. IUFRO Conf. Div. 5 Oxford, England. 1980;1.
 8. Cave ID, Walker JF. Stiffness of wood in fast-grown plantation softwoods: The influence of microfibril angle. Forest Products Journal. 1994;44(5):43-48.
 9. Philips EJ. The inclination of the fibrils in the cellwall and its relation to the compression strength of timber. Empire Forestry Journal. 1941;20:74-78.
 10. Hofmann T, Rétfalvi T, Albert L, Niemz P. Investigation of the chemical changes in the structure of wood thermally modified within a nitrogen atmosphere autoclave. Wood Research. 2008;53:85-98.
 11. Boonstra MJ, Rijdsdijk JF, Sander C, Kegel E, Tjeerdsmas B, Militz H, Van AJ, Stevens M. Microstructural and physical aspects of heat treated wood. Part 1. Softwoods 2006;8(3):193-208.
 12. Olufemi B, Ayanleye SO, Iyiola EA. Influence of thermal and chemical modification on the physical and mechanical properties of *Leucaena leucocephala* wood. Asian Journal of Advanced Research and Reports. 2018; 2(2):1-7.
 13. Diego VB, Jose OB. Effect of heat treatment on colour, weight loss, specific gravity and equilibrium moisture content of two low market valued tropical woods. Journal of Wood Science. 2014;59(2): 253-264.
 14. Sundqvist B. Color changes and acid formation in wood during heating. Doctoral Thesis, Lulea University of Technology, Lulea, Sweden. 2004; 45-50.
 15. Poncsac S, Kocaefe D, Bouazara M, Pitchette A. Effect of high temperature on mechanical properties of birch (*Betula papyrifera*) Wood Science and Technology. 2006;40(8):647-663. DOI: 10.1007/S00226-006-0082-9
 16. Esteves BM, Domingos IJ, Pereira HM. Pine wood modification by heat treatment in air. Bioresources. 2008;3(1):142-154.
 17. Boonstra M, Van AJ, Tjeerdsmas B, Kegel E. Strength properties of thermally modified softwoods and its relation to polymeric structural wood constituents. Annals of Forest Science. 2007;8:193-208.
 18. Ding T, Gu L, Liu X. Influence of steam Pressure on chemical changes of heat treated *Mongolian pine* wood. European Journal of Wood Products. 2011;69(1): 121-126. DOI: 10.1007/s00107-009-0406-01
 19. Lekounougou S, Kocaefe D. Effect of thermal modification temperature on mechanical properties, dimensional stability and biological durability of black spruce (*Picea mariana*). Wood Material Science and Engineering. 2014;9(2):59-66. DOI: 10.1080/17480272.2013.869256

© 2019 Iyiola et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:
The peer review history for this paper can be accessed here:
<http://www.sdiarticle3.com/review-history/48186>